

## DEVELOPMENT OF HTS MAGNETS FOR ACCELERATORS

K. Hatanaka\*, M. Fukuda, S. Hara, K. Kamakura, K. Shimada, Y. Yasuda, T. Yorita, Research Center for Nuclear Physics, Osaka University, Ibaraki, 567-0047 Osaka, Japan  
H. Ueda, Graduate School of Natural Science and Technology, Okayama University, 700-8530 Okayama, Japan

### Abstract

At RCNP, we have been developing magnets utilizing first generation HTS wires for this decade. HTS materials have advantages over LTS materials. Magnets can be operated at 20 K or higher temperature and cooled by cryo-coolers. The cooling structure becomes simpler and the cooling power of a cooler is higher. Owing to a large margin in operating temperature, it is possible to excite HTS magnets by AC or pulsed currents without quenching. After successful tests of proto type models, two magnets have been fabricated for practical use. Their design and operational performance of two models and the switching dipole magnet are discussed.

### INTRODUCTION

High critical temperature superconductor (HTS) materials were discovered in 1986 for the first time [1]. Since then, new HTS materials have been developed to achieve higher critical temperature. At present, two kinds of wires are commercially available having length over several hundred meters. They are based on Bi-2223 (the first generation wire) and REBCO (the second generation wire). Although HTS wires have several advantages over low critical temperature superconducting (LTS) wires, application studies of HTS wires have been limited so far. We have been developing magnets by applying the first generation wires for more than 10 years at the Research Center for Nuclear Physics (RCNP) of Osaka University.

Three model magnets were fabricated; a mirror coil for an ECR ion source [2], two sets of race track coils for a scanning magnet [3], and a 3T super-ferric dipole magnet having a negative curvature [4]. They were excited with AC and pulse currents as well as DC currents and their performance was investigated. After successful performance tests of proto type models, two magnets have been fabricated for practical use. A cylindrical magnet generates a magnetic field higher than 3.5 T at the center to polarized 210 neV ultra cold neutrons [5]. A switching dipole magnet is excited by pulse currents in order to deliver accelerated beams to two target stations by time sharing.

### MODEL MAGNETS

Air core magnets were fabricated and measured AC losses were compared to simulations. A two-dimensional scanning magnet was designed to model a compact system for the cancer treatment [3]. The magnet was designed to deflect 230 MeV protons by 80 mrd in both the

horizontal( $x$ ) and vertical ( $y$ ) directions as shown in Fig. 1. The iso center is at 1.25 m from the magnet and the irradiation field is 200 mm by 200 mm.

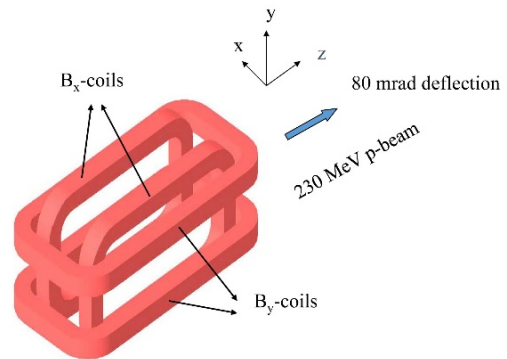


Figure 1. A schematic layout of the scanning magnet. They generate the horizontal ( $B_x$ ) and vertical ( $B_y$ ) field.

The magnet consists of two sets of two racetrack shaped coils. Specifications of coils are summarized in Table 1. Three double pancakes are stacked to form one coil. 9 mm thick brass cooling plates are inserted between pancakes. Figure 4 shows an assembled  $B_x$  coil which is vacuum impregnated by epoxy resin. Detailed structure of coil is described in ref. [3]. The HTS tape was supplied by American Superconductor Corporation. The  $I_c$  of the tape was measured at 77 K in a 10 m pitch before winding and was between 125 and 140 A corresponding to an electric field amplitude of 1  $\mu$ V/cm. The  $I_c$  of the each pancake and stacked coil were measured in a liquid  $N_2$  bath and were 56-62 and 40-43 A, respectively. Two single-stage GM refrigerators are used to cool coils and thermal shields separately. An AL330 of CRYOMECH, Inc. is used to cool coils and it has a cooling capacity of 45 W at the designed operating temperature 20 K. From the temperature dependence of the  $I_c(B_{\perp})$  characteristics of the tape,  $I_c$  is estimated to be 260 A.

Table 1: Specifications of Coils of the Scanning Magnet.

Inner size	$B_x$ : 150 mm x 300 mm $B_y$ : 150 mm x 380 mm
Cross-section	30 mm x 30 mm
Separation	70 mm
Maximum field at the center	0.6 T
HTS tape length/coil	$B_x$ : 420 m, $B_y$ : 460 m
Number of turns/coil	420 turns
Stacking/coil	3 Double pancakes
Inductance/coil	$B_x$ : 75 mH, $B_y$ : 92 mH

\* hatanaka@rcnp.osaka-u.ac.jp

A pair of coils are electrically connected in series and used as a scanning magnet excited by AC or pulsed currents. AC loss was measured by electrical method at 77 and 20 K [3]. There are several AC loss components observed in both LTS and HTS magnet [6, 7]. They are (1) hysteretic magnetization losses in the superconducting material, (2) dynamic resistance losses generated by a flux motion in the conductor, (3) coupling losses through the matrix and (4) eddy current losses in the matrix and metallic structures including cooling plates. In addition, there are (5) Ohmic losses at exciting currents above the critical current for HTS magnets. Each component shows a specific dependence on the frequency ( $f$ ), the amplitude of the external magnetic field ( $B$ ), and the transport current ( $I$ ). In the critical state model (CSM), the hysteresis loss per cycle is analytically formulated by Brant et al. [7] as follows,

$$Q_{hys} \propto 2\ln[\cosh(x)] - x \tanh(x) \quad (1)$$

where  $x=B/B_{c0}$  and  $B_{c0}=\mu_0 J_c d/\pi$ .  $J_c$  is the critical current density and  $d$  thickness of the conductor tape. Figure 2 shows AC losses of the two  $B_x$  coils in series measured at 20 K. Upper points are total losses scaled (left axis) and lower ones are losses per cycle (the right axis). The observed dissipated power per cycle is almost independent of the frequency of the transport current and the current dependence is well described by the formula (1).

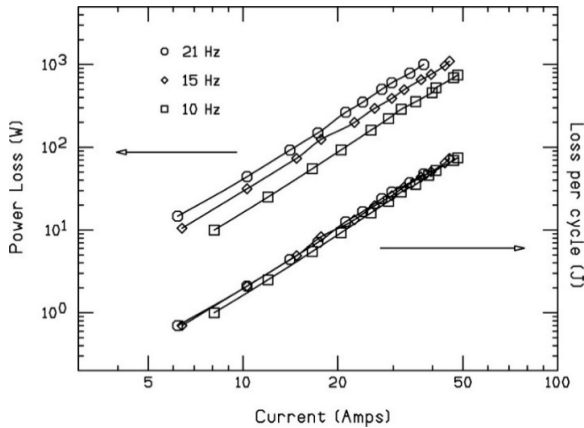


Figure 2. Measured AC losses at 20 K of the  $B_x$  coils in series. Data points at the same frequency are connected by line. Details are described in the text.

A dipole magnet was fabricated to investigate a potential application of HTS coils to synchrotron magnets [4]. It is a super-ferric magnet with race-track coils which have a negative curvature inside. The specification of the magnet is summarized in Table 2. The HTS tape is from Sumitomo Electric Industries, Ltd.  $I_c$  values of tape, double pancakes and stacked coils were measured at 77 K to be 160-189, 60-70 and 47-51 A, respectively. There were no damages observed during tape winding process. Figure 3 shows the assembled cold mass consisting of poles and coils. Coils are fixed to poles to withstand the radial electro-magnetic expansion force. Poles are laminated with 2.3 mm thick carbon steel plates to excite the magnet by pulse currents. Plates were bent before stack-

ing, welded to form a pole and finally annealed to remove the stress. The weight of the total cold mass is 250 kg. The magnet was successfully excited with the DC current of 300 A to generate 3 T at the center. Coil was also excited with pulsed current with the ramping speed of 100 A/s corresponding to 1 T/s.

Table 2: Specifications of the Model Dipole Magnet.

Magnet	Central bending radius	400 mm
	Bending angle	60 degrees
	Pole gap	30 mm
	Maximum field at the center	3 T
	Cold mass	250 kg
Coil	Number of turns/coil	300 turns

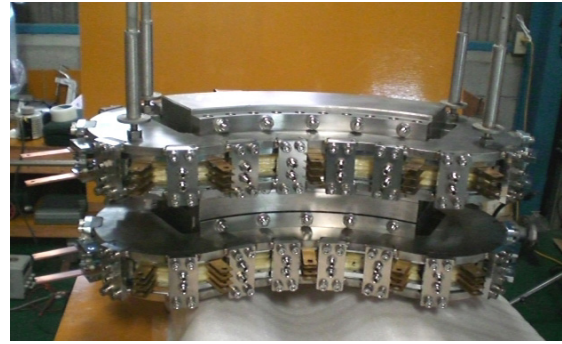


Figure 3. Photograph of the poles and coils of the model dipole magnet.

### SWITCHING DIPOLE MAGNET

We have more beam time requests than available at our cyclotron facility. To provide more beam to users, beam sharing between two target rooms are planned, for example at the UCN and muon production targets. To put it into practice, a conventional normal conducting magnet will be replaced by a pulsed magnet which is shown in Fig. 4. The magnet consists of a laminated yoke and two cryostats. B-2223 wire with reinforcing copper alloy (DI-BSCCO type HT-CA from Sumitomo Electric Industries, Ltd.) and insulation tape are wound into double pancake coil and are conduction cooled by 10 K GM cryocoolers (SRDK-408S2 from Sumitomo Heavy Industries, Ltd.). The typical cooling power of the 2nd stage is 16 W at 20 K and 2 W at 7.5 K. Figure 5 shows the structure of a cryostat. Each cryostat contains a radiation shield thermally connected to the 1st

Table 3: Design Parameters of the HTS Dipole Magnet

Coil	Inner size	1,142 mm x 580 mm
	Number of DP	2
	Numbers of turns	256 x 2
	Inductance	2.5 H
Magnet	Temperature	< 20 K
	Rated current	200 A
	Field at center	1.6 T



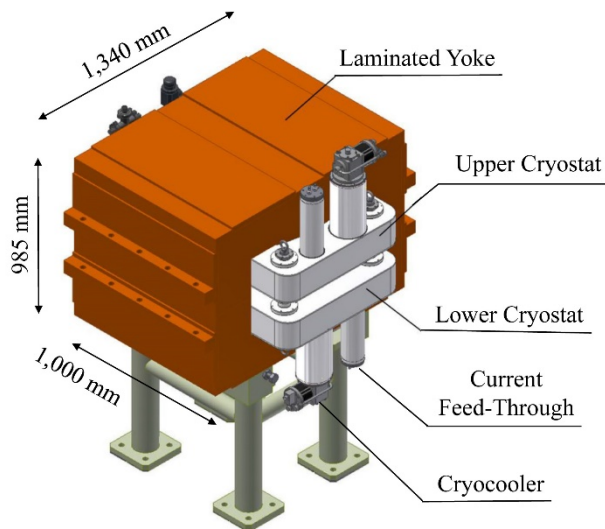


Figure 4: HTS switching dipole magnet..

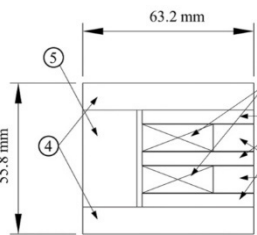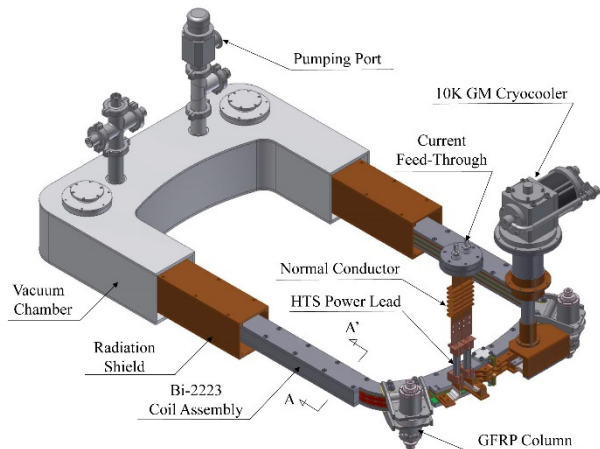

No.	Description	Material
1	Bi-2223 DPC	
2	Winding Frame	Stainless Steel
3	Cooling Plate	Copper
4	Reinforcing Plate	Stainless Steel
5	Reinforcing Bar	Stainless Steel

Figure 5: Structure of a cryostat (upper panel) and A-A' cross sectional view of and major component list of the coil assembly (lower panel).

Figure 6 shows the initial cooling performance of the magnet. It takes 50 hours to cool the whole magnet down to operational temperature. Thermometer B is measured near the connecting point to a cryocooler and A at the far end of the coil assembly. For time sharing of a beam, rapid excitation is required. The magnet's iron core is laminated and the power supply is designed to perform 20 A/s ramping with 2.5 H of the coil's inductance. A temperature history during a pattern operation is shown in Fig. 7. Coil temperature stays in the operating temperature with a large margin during 30-second exiting and 60-second degaussing pattern. The saturated temperature

after two hours of operation is lower than 8.5 K. The result confirmed the thermal design. To provide precise beam switching, the highly stable field strength is required. We are performing systematic measurements of the magnetic fields to find the optimum conditions.

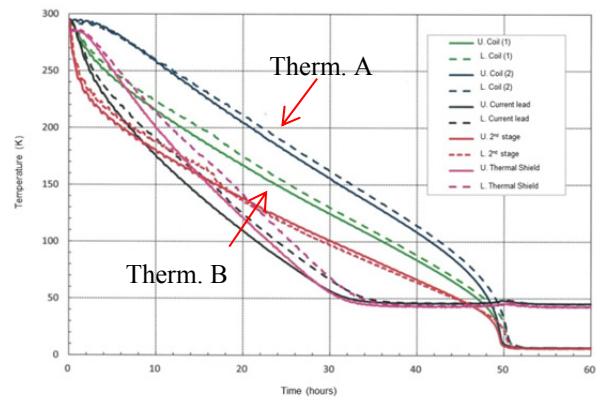


Figure 6: Initial cooling performance of the HTS magnet.

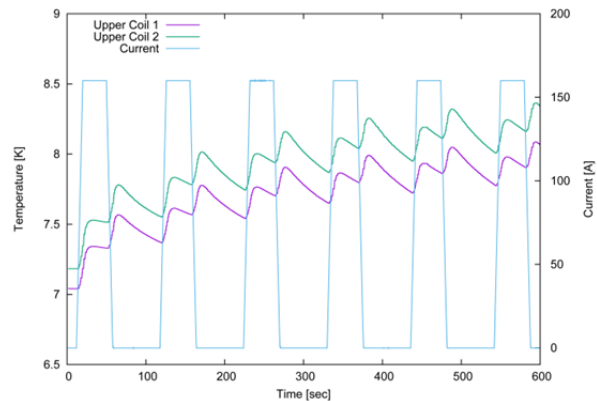


Figure 7: Temperature of upper coil during pattern operation.

## REFERENCES

- [1] J. G. Bednorz and K. A. Müller, *Physical B* 64 (1986) 189.
- [2] K. Hatanaka, S. Ninomiya, Y. Sakemi, T. Wakasa, T. Kawaguchi, N. Takahashi, *Nucl. Instr. Meth. in Phys. Res. A* 571 (2007) 583-587.
- [3] K. Hatanaka, J. Nakagawa, M. Fukuda, T. Yorita T..Saito, Y. Sakemi, T. Kawaguchi, K. Noda, *Nucl. Instr. Meth. in Phys. Res. A* 616 (2010) 16-20.
- [4] K. Hatanaka, et al., in *Proc. of IPAC'12*, New Orleans, Louisiana, May 2012, paper TUOAC02, p. 1095.
- [5] K. Hatanaka, et al., in *Proc. of IPAC'13*, Shanghai, China, May 2013, paper THPME007, p. 3522.
- [6] C. M. Friend, "AC Losses of HTS Tapes and Wires", *Studies of High Temperature Superconductors*, A. V. Narlikar, Ed. New York: Nova Science Publishers, 2000, vol. 32, pp. 1-61.
- [7] E. H. Brandt and M. Indenbom, *Phys. Rev. B* 48 (1993) 12893-12906.